

Contents list available at **IJND**
International Journal of Nano Dimension

Journal homepage: www.IJND.ir

CaF₂ nanoparticles: Synthesis and characterization

K. Tahvildari¹
M. Esmaeili pour^{1,*}
Sh. Ghammamy²
H. Nabipour²

¹Department of Chemistry,
Islamic Azad University, North
Tehran Branch, Tehran, Iran.

²Department of Chemistry,
Islamic Azad University,
Takestan Branch, Takestan,
Iran.

ABSTRACT

The aim of the present study was to prepare nano-sized calcium fluoride (CaF₂). Calcium fluoride nanoparticles were synthesized by CaCl₂.6H₂O and ammonium fluoride. Nanoparticles were synthesized by co-precipitation method. The synthesized nanocrystals were characterized by X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FTIR), scanning electron microscopy (SEM). The crystallite size estimated using Scherer's formula was found to be in the range of 20–30nm for nanocrystals synthesized by this method. The morphological features as studied using SEM revealed that the nanoparticles were agglomerated, crispy with porous.

Keywords: *Synthesis; Characterization; Nanoparticles; Calcium fluoride.*

Received: 01 September 2011
Accepted: 07 November 2011

INTRODUCTION

The synthesis of inorganic nano- and micro materials with well-defined and controllable morphologies has stimulated considerable attention, because it is well known that the properties of the materials closely interrelate with geometrical factors such as morphology, dimensionality, and the size [1–5]. It has been well-established that alkali earth metal (AEM) fluorides MF₂, where M = Ca, Sr or Ba, should be very attractive host crystals for some applications. These applications may be as Ln and transition metal laser activators since they possess a broad optical transparency region, moderate Raman gain coefficients, relatively small linear and non-linear refractive indices, and rather flat curvature of the refractive index dispersion over a wide wavelength range in the near IR. Under such unique optical properties and rather reasonable physical characteristics one may expect high peak laser action. That is why these single AEM fluorides doped by some rare-earth (RE) trivalent ions appeared objects of intensive investigations from the very beginning of the last decade of 20th century. The ambitious purpose was to establish whether these materials were suitable for use as effective laser-pumped amplifier media [6]. Furthermore Calcium fluoride (CaF₂) and “CaF₂-like” materials are of significant interest in dentistry due to their roles as labile fluoride (F) reservoirs in cavities prevention.

* Corresponding author:
Mahnaz Esmaeilipour
Islamic Azad University, North
Tehran Branch, Department of
Chemistry, Tehran, Iran.
Tel +98 9361157726
Fax +98 28205270145
Email m.esmaeilipour@yahoo.com

Low concentration of F used in oral fluids derived as F reservoirs formed by the use of F dentifrices and rinses, have been shown to have a profound effect on the progression of dental cavities [7–9]. However reports on synthesis of fluoride nanoparticles are limited. CaF_2 nanoparticles were synthesized by different methods such as sol–gel method [10–15], solvothermal process [16,17], reverse micelle method [18,19], different precipitation methods [20–23], and flame synthesis [24]. In the present work CaF_2 nanoparticles are prepared by co-precipitation method and are characterized by XRD, SEM, IR techniques.

EXPERIMENTAL

Material and methods

Calcium fluoride, ethanol and ammonium fluoride were purchased from Merck Company. The XRD measurements of synthesized samples were carried out using a Philips X-pert PRO powder diffractometer with $\text{Cu-K}\alpha$ radiation ($\lambda = 1.54060 \text{ \AA}$) in the scan range $0\text{--}100^\circ$. The morphology of synthesized sample was studied using scanning electron microscopy (Philips-XL30) by a sputtering technique with gold as covering contrast material. The IR spectra were recorded using Bruker spectrometer with KBr pellets in the range from 400 to 4000 cm^{-1} .

Synthesis of nanoparticles

Calcium chloride hexahydrate ($\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$), ammonium fluoride (NH_4F) were

prepared in ethanol for synthesis of CaF_2 nanoparticles by co-precipitation method. CaCl_2 (0.01 mol) was dissolved in 50 ml ethanol taken in 250 ml conical flask. NH_4F (0.02 mol) was added into the flask under vigorous stirring on a magnetic stirrer. The mixed solution was stirred for 3 h to gradually transform the transparent reaction mixture into opaque white suspension. Then, the mixture was centrifuged for 15 min at 4000 rpm and washed three times with water via centrifugation to eliminate the residual chloride and the ammonium ions. Finally the solid product was extracted and then kept in a desiccator over P_2O_5 .

RESULTS AND DISCUSSION

Powder X-ray diffraction (XRD)

The XRD patterns of CaF_2 nanoparticles is shown in Figure 1, and all of the diffraction peaks can be readily indexed to a pure cubic phase (space group: $\text{Fm}\bar{3}\text{m}$ (225)) [25], which are in agreement with the standard values for cubic CaF_2 (JCPDS Card no. 87 - 0971). The XRD results indicate that the products we obtained were CaF_2 nanoparticles. The XRD pattern presents broad peaks revealing the small crystallite size of the synthesized samples. The nanoparticles size was calculated from the full width at half maximum (FWHM) technique using Scherer's formula $D = K\lambda / (\beta \cos \theta)$ where K is the constant (0.99), λ is the wavelength of $\text{Cu-K}\alpha$ (1.54 \AA) line, β is the FWHM and θ is the diffraction angle. The nanoparticles size obtained in the range $20\text{--}30 \text{ nm}$.

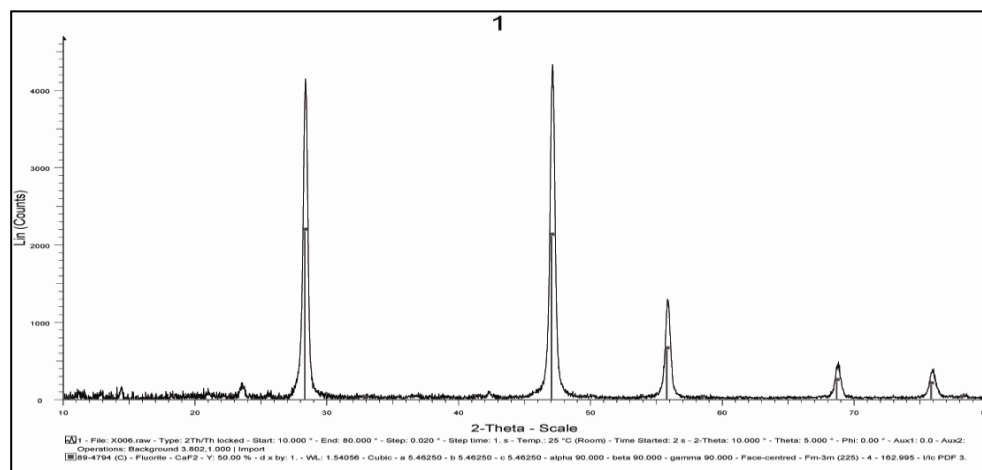


Fig. 1. X-ray diffraction spectrum of CaF_2 nanoparticles

Scanning electron microscopy (SEM)

The SEM images are shown in Figure 2. The larger particles exhibited numerous spherical perturbances on the surface, suggesting that they were formed during the precipitation process through fusion of the much smaller particles. The prepared products were agglomerated from few microns to a few tens of microns, fluffy and porous.

Fourier transform infrared spectrum (FTIR)

Although the synthesized CaF_2 was a white powder, its purity was further examined by means of FT-IR spectrometry. The peak at 443 cm^{-1} in the FT-IR spectrum in Figure 3 was assigned to the Ca-F stretching vibration of CaF_2 . The spectrum shows strong IR absorption bands at $\sim 3423\text{ cm}^{-1}$ which is characteristic of H-O-H bending of the H_2O molecules revealing the

presence hydroxyl groups in the as prepared sample [26, 27].

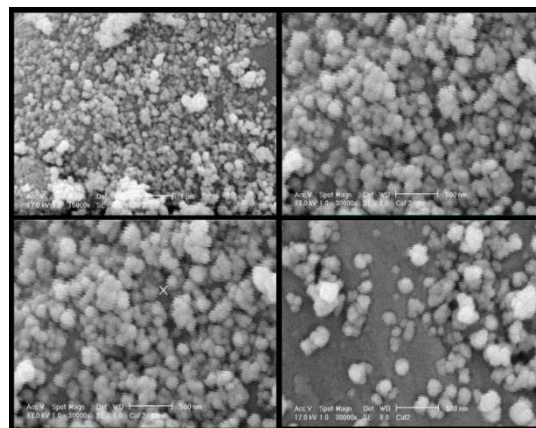


Fig. 2. SEM images of CaF_2 nanoparticles synthesized by co-precipitation method

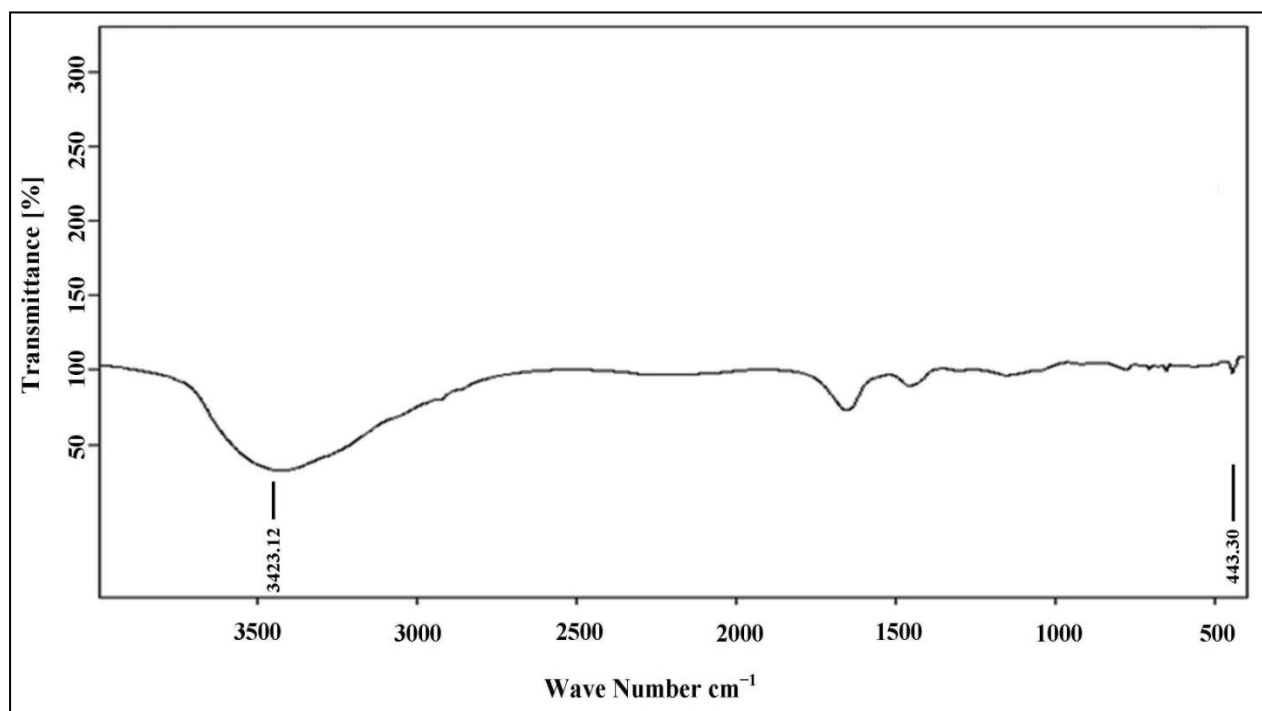


Fig. 3. FT-IR spectrum of CaF_2 nanoparticles

CONCLUSION

In conclusion, the current report describes the synthesis of pure phase CaF₂ nanoparticles in uniform diameter of ~20 nm by co-precipitation method and characterized by XRD, SEM, IR, and optical absorption. It is noteworthy that the co-precipitation method is effective for obtained pure phase nanomaterials with controllable size, uniform morphology and shape. This method has several advantages such as: wide range of achievable compositions, lower processing temperature, easier composition control, and better chemical homogeneity of the product. Resulting nanocrystals have been characterized using spectroscopy data. The nano-CaF₂ can be used as an effective anticaries agent in increasing the labile F concentration in oral fluid and thus enhance the tooth remineralization. It can also be very useful in the treatment for the reduction of dentin permeability. Also fluorides are well known for their antimicrobial activity, The CaF₂ nanoparticles can be used as an antimicrobial compound in various cases.

REFERENCES

- [1] Peng, X., Manna, L., Yang, W., Wickham, J., Scher, E., Kadavanich, A., Alivisatos, A.P., (2000), Shape control of CdSe nanocrystals, *Nature*, 404, 59-61.
- [2] Colfen, H., Mann, S., *Angew.*, (2003), Higher-order organization by mesoscale self-assembly and transformation of hybrid nanostructures, *Chem. Int. Ed.*, 42, 2350-2365.
- [3] Lao, J.Y., Wen, J.G., Ren, Z.F., (2002), Hierarchical ZnO nanostructures, *Nano Lett.*, 2, 1287-1291.
- [4] Xie, Y., Huang, J.X., Li, B., Liu, Y., Qian, Y.T., (2000), A Novel Peanut-like Nanostructure of II-VI Semiconductor CdS and ZnS, *Adv. Mater.*, 12, 1523.
- [5] Quan, Z.W., Yang, J., Yang, P.P., Wang, Z.L., Li, C.X., Lin, J., *Cryst.*, (2000), Facile synthesis and characterization of single crystalline Bi₂S₃ with various morphologies, *Growth Des.*, 8, 200.
- [6] Kaminskii, A.A., (1981 and 1990), *Laser Crystals, Their Physics and Properties.*, Springer, Berlin, 139-155.
- [7] Rølla G., (1988), Preparation and Properties of Nano-sized Calcium Fluoride for Dental Applications, *Acta Odontol Scan*, 46, 341-345.
- [8] Lagerlof, F., Ekstrand, J., Rølla, G., (1988), Effect of fluoride addition on ionized calcium in salivary sediment and in saliva., *Scand J Dent Res*, 96, 399-404.
- [9] Rølla, G., Saxegard, E., (1990), Critical evaluation of the composition and use of topical fluorides with emphasis on the role of calcium fluoride in caries inhibition, *J Dent Res*, 69(Special Issue), 780-785.
- [10] Fujihara, S., Kadota, Y., Kimura, T., (2002), Role of organic additives in the sol-gel synthesis of porous CaF₂ anti-reflective coatings, *J. Sol-Gel Sci. Technol.*, 24, 147-154.
- [11] Hong, B.-C., Kawano, K., (2006), Reduction of Eu²⁺-activated nanoparticles by unique TCRA treatment, *J. Alloys Compd.*, 838, 408-412.
- [12] Zhou, L., Chen, D., Luo, W., Wang, Y., Yu, Y., Liu, F., (2007), Transparent glass ceramic containing Er³⁺:CaF₂ nano-crystals prepared by sol-gel method, *Mater. Lett.*, 61, 3988.
- [13] Hong, B.-C., Kawano, K., (2008), Luminescent Antireflective Coatings with Disordered Surface Nanostructures Fabricated by Liquid Processes, *Opt. Mater.*, 30, 952.
- [14] Patil, P.T., Dimitrov, A., Radnikb, J., Kemnitz, E., (2008), Sol-gel synthesis of metal fluoride supported Pd catalysts for Suzuki coupling, *J. Mater. Chem.*, 18, 1632.
- [15] Hong, B.C., Kawano, K., (2008), *J. Alloys Compd.*, 451, 276-279.
- [16] Kumar, G.A., Chen, C.W., Ballato, J., Riman, R.E., (2007), Optical Characterization of Infrared Emitting Rare-Earth-Doped Fluoride Nanocrystals and Their Transparent Nanocomposites, *Chem. Mater.*, 19, 1523.
- [17] Zhang, X., Quan, Z., Yang, J., Yang, P., Lian, H., Lin, j., (2008), Solvothermal synthesis of well-dispersed MF(2) (M = Ca, Sr, Ba) nanocrystals and their optical properties. , *J. Nanotechnology*, 19(7):075603.
- [18] Bensalah, A., Mortier, M., Patriarcheb, G., Gredin, P., Vivien, D., (2006), Synthesis and optical characterizations of undoped and rare

- earth doped CaF_2 nano-particles, *J. Solid State Chem.*, 179, 2636.
- [19] Aubry, P., Bensalah, A., Gredin, P., Patriarche, G., Vivien, D., Mortier, M., (2009), Synthesis and optical characterizations of Yb-doped CaF_2 ceramics, *Opt. Mater.*, 31, 750.
- [20] Sun, X., Li, Y., (2003), *Chem. Commun.*, 14, 1768-1769.
- [21] Wang, F., Fan, X., Pi, D., Wang, M., (2005), Synthesis and luminescence behavior of Eu-doped CaF_2 nanoparticles, *Solid State Commun.*, 133, 775.
- [22] Mortier, M., Bensalah, A., Dantelle, G., Patriarche, G., Vivien, D., (2007), doped oxyfluoride glass-ceramics and fluoride ceramics: Synthesis and optical properties, *Opt. Mater.*, 29, 1263.
- [23] Wang, L., Wang, B., Wang, X., Lu, W., (2007), Tribological investigation of CaF_2 nanocrystals as grease additives. *Tribol. Int.*, 40, 1179-1185.
- [24] Grass, R.N., Stark, W.J., (2005), Flame synthesis of calcium-, strontium-, barium fluoride nanoparticles and sodium chloride, *Chem. Commun.*, 1767.
- [25] Gerward, L., Olsen, J.S., Streenstrup, S., Malinowski, M., Asbrink, S., Waskowska, A., (1992), X-ray diffraction investigations of CaF_2 at high pressure, *J. Appl. Crystallogr.*, 25, 578.
- [26] Zhou, L., Chen, D., Luo, W., Wang, Y., Yu, Y., Liu, F., (2007), Transparent glass ceramic containing $\text{Er}^{3+}:\text{CaF}_2$ nano-crystals prepared by sol-gel method, *Mater. Lett.*, 61, 3988.
- [27] Huang, X.H., Chen, Z.H., (2005), study of nanocrystalline NiFe_2O_4 in a silica matrix, *Mater. Res. Bull.*, 40, 105.

